

Investigation of the Spin-Peierls transition in CuGeO₃ by Raman scattering

P. Lemmens, B. Eisener, M. Brinkmann, L.V. Gasparov,
G. Güntherodt, P.v. Dongen⁺, W. Richter*,
M. Weiden*, C. Geibel*, F. Steglich*

February 1, 2008

2. Physikalisches Institut, RWTH Aachen,

⁺Institut für Theoretische Physik, RWTH Aachen, 52056 Aachen, Germany

*Institut für Technische Physik, TH Darmstadt, 64289 Darmstadt, Germany

Proceedings of SCES'1995, Goa, India, to be published in Physica B (1996)

Abstract

Raman experiments on the spin-Peierls compound CuGeO₃ and the substituted (Cu_{1-x}Zn_x)GeO₃ and Cu(Ge_{1-x}Ga_x)O₃ compounds were performed in order to investigate the response of specific magnetic excitations of the one-dimensional spin-1/2 chain to spin anisotropies and substitution-induced disorder. In pure CuGeO₃, in addition to normal phonon scattering which is not affected at all by the spin-Peierls transition, four types of magnetic scattering features were observed. Below T_{SP}=14 K a singlet-triplet excitation at 30 cm⁻¹, two-magnon scattering from 30 to 227 cm⁻¹ and folded phonon modes at 369 and 819 cm⁻¹ were identified. They were assigned by their temperature dependence and lineshape. For temperatures between the spin-Peierls transition T_{SP} and approximately 100 K a broad intensity maximum centered at 300 cm⁻¹ is observed. The temperature dependence of this intensity is similar to the behavior of lattice fluctuations recently observed in an electron diffraction study. This scattering is attributed to dynamical spin-Peierls fluctuations of the weakly or non-static dimerized spin chain.

1

¹Keywords: spin-Peierls transition, CuGeO₃, spin-1/2 chains, singlet-triplet excitation, Raman scattering

Author for correspondence:

Dr. P. Lemmens, 2. Physikalisches Institut RWTH Aachen, 52056 Aachen, Germany,
Tel.: 0241-807113, Fax.: 0241-8888306 Email: lemmens@sun1.phys2.rwth-aachen.de

1 Introduction

It has been of continued interest to understand the physical properties of low-dimensional quantum spin systems to clarify the relation between dimensionality or anisotropies and low energy excitations. The recently discovered spin-Peierls (SP) transition in the compound CuGeO_3 [1], resulting from the coupling of an antiferromagnetic spin-1/2 Heisenberg chain to a three-dimensional lattice system, is a model system in this respect. The magnetic susceptibility of CuGeO_3 shows a broad maximum at about 60 K and an exponential, isotropic decrease below $T_{SP}=14$ K, reflecting the effect of quantum fluctuations above T_{SP} and the continuous dimerization of the Heisenberg chain below T_{SP} [2]. By inelastic neutron scattering the dispersion relations of magnetic excitations, the anisotropy of the exchange coupling and the singlet-triplet transition $\Delta(q \approx 0) = 16.8 \text{ cm}^{-1}$ of the dimerized Heisenberg chain were determined [3,4]. For temperatures above T_{SP} specific heat measurements show that the magnetic entropy reaches $R \ln 2$ not until $T \approx 150$ K is approached [5]. Additional hints toward strong lattice fluctuations along the spin-1/2 chains exist in electron diffraction experiments for temperatures $T \leq 100$ K [6]. By Raman scattering, phonon and two-magnon scattering and the singlet-triplet excitation at $2\Delta = 30 \text{ cm}^{-1}$ were identified [7, 8].

2 Experimental

Polycrystalline samples of the stoichiometry $(\text{Cu}_{1-x}\text{Zn}_x)\text{GeO}_3$ and $\text{Cu}(\text{Ge}_{1-x}\text{Ga}_x)\text{O}_3$ with x ranging from 0 to 0.07 and 0.04, respectively, were prepared by standard solid state reaction. Single crystals of CuGeO_3 were grown by slow cooling of a stoichiometric mixture. The samples were characterized by magnetic susceptibility measurements and x-ray diffraction. The magnetic susceptibility shows at the lowest temperatures measured (≈ 2 K) a small upturn, pointing to a negligible content of paramagnetic impurities, which may result from disrupted Cu-chains.

3 Results and Discussion

In Fig.1 the scattering intensity of single crystalline CuGeO_3 is shown in (z,z) -geometry, i.e. with polarization of the incident and scattered light both parallel to the Cu-chains (c -axis of the crystal lattice). Below $T_{SP}=14$ K there appears additional scattering intensity at 30, 105, 227, 369 and 819 cm^{-1} . The peak positions and widths of the modes at 30, 227 and 369 cm^{-1} are given in Fig. 2. Comparing the scattering intensity with a two-magnon density of states calculated in Heisenberg spin-wave approximation we get reasonable agreement with the measured intensity in the interval 30-300 cm^{-1} . As fit parameters we used the following exchange coupling constants $J_c = 68.6 \text{ cm}^{-1}$, $J_b = 6.1 \text{ cm}^{-1}$, $J_a = -0.5 \text{ cm}^{-1}$ and $J' = 10.4 \text{ cm}^{-1}$. The coupling constants J_c , J_b , J_a along the principal axes of the compound and J' (giving the alternating exchange along the Cu-chain with $J_{1/2} = \pi/2 \cdot J_c \pm J'$) show quantitative agreement with neutron scattering and susceptibility measurements ($J_c^{sus} = 61 \text{ cm}^{-1}$) [1,3]. However, the sharp peak at 30 cm^{-1} does neither fit in intensity nor in its temperature

dependence into the concept of spin waves.² This is shown in Fig. 2 by comparing its temperature dependence and width with the two-magnon scattering at 227 cm^{-1} and the dimerization-induced folded phonon mode at 369 cm^{-1} . The singlet-triplet excitation shows a drastic frequency shift and linewidth broadening with increasing temperature while the other modes disappear without any renormalizations in frequency or linewidth. This large broadening comparable with the self-energy of the excitation is expected for magnetic excitons if their degree of localization depends strongly on the order parameter, i.e. the alternation of the exchange coupling [9]. In the noninteracting-dimer limit excitons with a bound character are well defined excitations. However, due to the weak exchange coupling and the inherent instability of the spin-chain a more dynamical pairing description of the triplet states comparable with a spin-Peierls t-J-model is suggested leading to weak or non-static dimerization [10,11]. A critical test of this state would be the observation of spin and lattice fluctuations of the Heisenberg chain above T_{SP} with characteristic energies higher than the exchange coupling. Electron diffraction and specific heat measurements both show fluctuation contributions for temperatures $T \leq 150\text{ K}$ [5,6]. Further hints for unusual spin dynamics above T_{SP} are resolved by Cu NQR and interpreted in a similar way [12]. Here we present evidence for these fluctuations in form of a broad maximum centered near 300 cm^{-1} with a total width of 300 cm^{-1} , as shown by the inset of Fig. 3. The energy corresponding to this maximum is a factor of 3-4 higher than the exchange coupling in the dimerized state and may therefore not be interpreted as two-magnon scattering. Its scattering contribution vanishes rapidly in the dimerized state leading to a redistribution of intensity to lower energy for $T \leq T_{SP}$. At higher temperatures, $T \geq 100\text{ K}$ the maximum is smeared out to higher and lower frequencies. In Fig. 3 we show the temperature dependence of this intensity, which was determined by subtracting the intensity at 520 cm^{-1} from the intensity at the maximum (determined at 256 cm^{-1}). This subtraction excludes phonon scattering and small changes of the laser power. The intensity of the assigned fluctuation contributions in Fig.3 shows a maximum at T_{SP} and a sharp drop toward lower temperatures.

Further evidence for the non-static evolution of the spin-Peierls phase may result from the strong sensitivity of T_{SP} to any substitution in the Cu-chains [13]. Our Raman experiments show that the singlet-triplet excitation at $2\Delta=30\text{ cm}^{-1}$ exhibits the strongest sensitivity to substitutions. For Ga-contents larger than $x=0.03$ and Zn-contents larger than $x=0.01$ this scattering intensity vanishes completely while the folded phonon modes still survive. The latter intensity vanishes if the spin-Peierls state is completely destroyed by substitution. For smaller substitution levels a reduction of the energy of the singlet-triplet excitation up to 20% is observed without any broadening of its lineshape. This is related to the pinning of spin fluctuations at the substitution site [8].

This work was supported by DFG through SFB 341, SFB 252 and by BMBF FKZ 13N6586

²Note added after proof: This intensity and the continuum at $\approx 300\text{ cm}^{-1}$ was modeled recently by calculating frustration induced Raman scattering of a one-dimensional Heisenberg chain, see: V.N. Muthukumar, et al., Frustration induced Raman scattering in CuGeO_3 .

4 References

- [1] M. Hase et al., Phys. Rev. Lett. 70 (1993) 3651 and Phys. Rev. B48, 13 (1993) 9616
- [2] J.C. Bonner and M.E. Fisher, Phys. Rev. 135 (1964) A640
- [3] M. Nishi, O. Fujita, J. Akimitsu, Phys. Rev. B50, 9 (1994) 6508
- [4] O. Fujita et al., Phys. Rev. Lett. 74, (1994) 1677
- [5] M. Weiden, J. Köhler, G. Sparn, M. Köppen, M. Lang, C. Geibel, F. Steglich, to be published
- [6] C.H. Chen and C-W.Cheong, Phys. Rev. B51, 10 (1995) 6777
- [7] H. Kuroe et al., Phys. Rev B22, 50 (1994) 16468
- [8] P.Lemmens, B.Eisener, M.Brinkmann, L.V. Gasparov, G. Güntherodt, P.v. Dongen, W.Richter, M.Weiden, C. Geibel, F.Steglich, to be published
- [9] J.C. Bonner, H.W.J. Blöte, Phys. Rev. B25, 11 (1982) 6959
- [10] M. Imada, J. Phys. Soc. Jpn. 60 (1991) 1877 and 61 (1992) 423
- [11] P.W. Anderson, Mater. Res. Bull. 8 (1973) 153
- [12] J. Kikuchi, et al., J. Phys. Soc. Japan, 63, 3 (1994) 872
- [13] S.B. Oseroff, et al., Phys. Rev. Lett. 74, 8 (1995) 1450

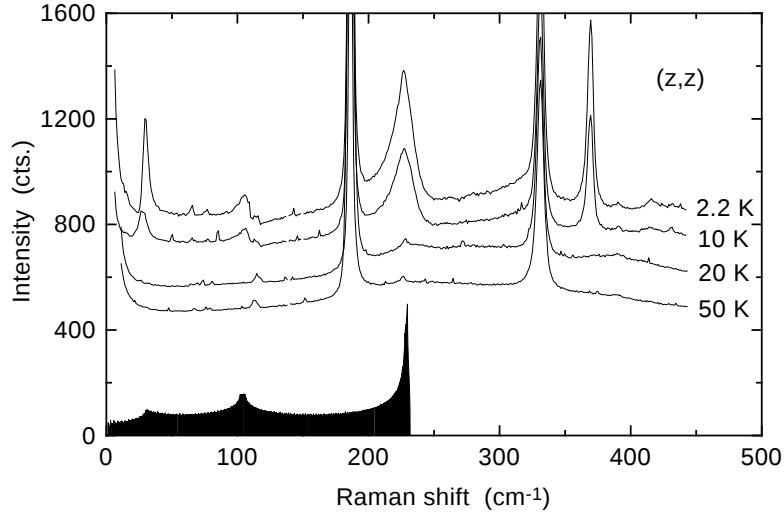


Figure 1: Raman scattering intensities of single crystalline CuGeO₃ at 2.2, 10, 20 and 50 K. The curves are shifted by an overall offset of 400 counts and by 100 counts between the individual spectra. The dark area shows a calculation of the two-magnon density of states in the spin-Peierls phase with the exchange coupling constants $J_c=68.6 \text{ cm}^{-1}$, $J_b=6.1 \text{ cm}^{-1}$, $J_a=-0.5 \text{ cm}^{-1}$ and $J'=10.4 \text{ cm}^{-1}$.

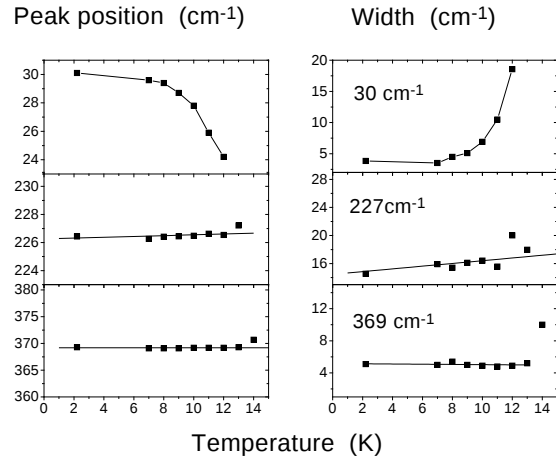


Figure 2: Peak position and width (FWHM) of the singlet-triplet excitation at 30 cm^{-1} , the two-magnon scattering at 227 cm^{-1} and a folded phonon mode at 369 cm^{-1} as a function of temperature. The lines are guides to the eye.

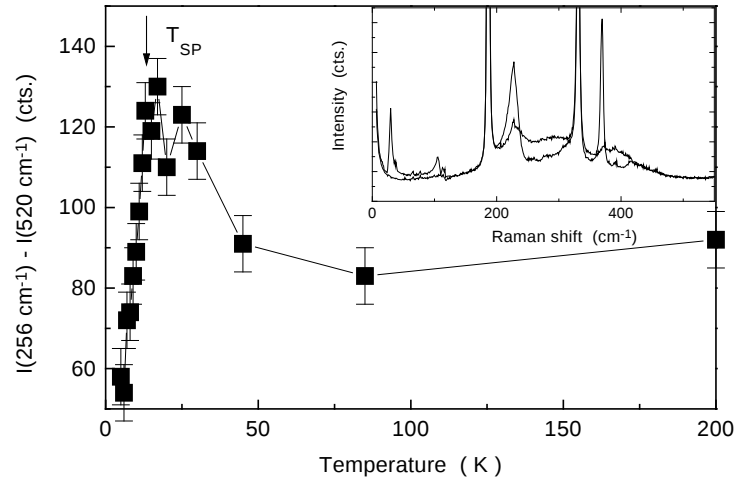


Figure 3: Scattering intensity of the broad maximum near 300 cm^{-1} as a function of temperature determined by subtracting the intensity at 520 cm^{-1} from the intensity at 256 cm^{-1} . The line is a guide to the eye. The inset shows Raman spectra at 7 K (lower curve) and 15 K (upper curve).